


# ASTM B232


## Aluminium Conductor Steel Reinforced(ACSR)

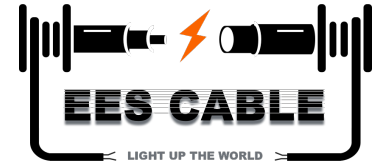

Co de Na me	Area				Equivale nt copper area		Stranding and wire diameter		Approx. overall diameter	Weight			Rated Strengt h	Maximum dc resistance at 20 °C
	Aluminium		Steel	Total	AWG or MCM	mm <sup>2</sup>	Aluminium	Steel		Aluminium	Steel	Total		
	AWG or MCM	mm <sup>2</sup>	mm <sup>2</sup>	mm <sup>2</sup>			mm	mm	mm	kg/km	kg/km	kg/km	kN	Ω/km
TURKEY	6	13.30	2.22	15.52	8	8.39	6/1.68	1/1.68	5.04	36.5	17	54	5.28	2.1499
THRUSH	5	16.83	2.81	19.64	7	10.58	6/1.89	1/1.89	5.67	46.0	22	68	6.68	1.6987
SWAN	4	21.18	3.53	24.71	6	13.29	6/2.12	1/2.12	6.36	58.0	27	85	8.30	1.3501
SWANATE	4	21.12	5.35	26.47	6	13.29	7/1.96	1/2.61	6.53	58.0	42	100	10.68	1.3539
SWALLOW	3	26.69	4.45	31.14	5	16.77	6/2.38	1/2.38	7.14	73.0	35	108	10.21	1.0712
SPARROW	2	33.59	5.60	39.19	4	21.16	6/2.67	1/2.67	8.01	92.0	44	136	12.69	0.8512
SPARATE	2	33.54	8.55	42.09	4	21.16	7/2.47	1/3.30	8.24	92.0	67	159	16.14	0.8525
ROBIN	1	42.41	7.07	49.48	3	26.65	6/3.00	1/3.00	9.00	116.0	55	171	15.81	0.6742
RAVEN	1/0	53.52	8.92	62.44	2	33.61	6/3.37	1/3.37	10.11	147.0	69	216	19.35	0.5343
QUAIL	2/0	67.33	11.22	78.55	1	42.39	6/3.78	1/3.78	11.34	185.0	87	272	23.27	0.4247
PIGEON	3/0	85.12	14.19	99.31	1/0	53.48	6/4.25	1/4.25	12.75	234.0	110	344	29.42	0.3359
PENGUIN	4/0	107.20	17.87	125.10	2/0	67.42	6/4.77	1/4.77	14.31	294.0	139	433	36.54	0.2667
WAXWING	266.8	135.00	7.50	142.50	3/0	85.03	18/3.09	1/3.09	15.45	372.0	59	431	30.27	0.2118
OWL	266.8	135.40	17.62	153.00	3/0	85.03	6/5.36	7/1.79	16.09	371.0	138	512	42.95	0.2112
PARTRIDGE	266.8	134.90	21.99	156.90	3/0	85.03	26/2.57	7/2.00	16.28	373.0	172	545	50.23	0.2141
OSTRICH	300	152.20	24.71	176.90	189	95.48	26/2.73	7/2.12	17.28	422.0	193	615	56.55	0.1897
MERLIN	336.4	170.20	9.46	179.70	4/0	107.23	18/3.47	1/3.47	17.35	469.0	74	543	38.17	0.1688
LINNET	336.4	170.60	27.83	198.40	4/0	107.23	26/2.89	7/2.25	18.31	473.0	217	690	62.76	0.1693
ORIOLE	336.4	170.50	39.78	210.30	4/0	107.23	30/2.69	7/2.69	18.83	474.0	311	785	77.43	0.1698
CHICKADEE	397.7	200.90	11.16	212.10	250	126.45	18/3.77	1/3.77	18.85	555.0	87	642	43.37	0.1430
BRANT	397.5	201.60	26.13	227.70	250	126.45	24/3.27	7/2.18	19.62	558.0	204	762	64.72	0.1433
IBIS	397.5	201.30	32.73	234.00	250	126.45	26/3.14	7/2.44	19.88	558.0	256	814	72.05	0.1434
LARK	397.5	200.90	46.88	247.80	250	126.45	30/2.92	7/2.92	20.44	558.0	367	925	90.30	0.1441

# ASTM B232


## Aluminium Conductor Steel Reinforced(ACSR)

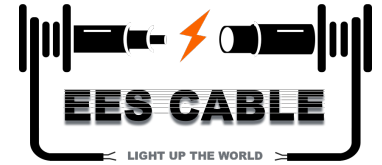

Code Name	Area				Equivalent copper area		Stranding and wire diameter		Approx. overall diameter	Weight			Rated Strength	Maximum dc resistance at 20 °C
	Aluminium		Steel	Total			Aluminium	Steel		Aluminium	Steel	Total		
	AWG or MCM	mm <sup>2</sup>	mm <sup>2</sup>	mm <sup>2</sup>	AWG or MCM	mm <sup>2</sup>	mm	mm	mm	kg/km	kg/km	kg/km	kN	Ω/km
PELICAN	477	242.30	13.46	255.80	300	152.26	18/4.14	1/4.14	20.70	668.0	105	773	52.30	0.1186
FLICKER	477	241.60	31.40	273.00	300	152.26	24/3.58	7/2.39	21.49	669.0	245	914	76.78	0.1195
HAWK	477	241.60	39.49	281.10	300	152.26	26/3.44	7/2.68	21.80	669.0	306	975	86.73	0.1195
HEN	477	241.30	56.30	297.60	300	152.26	30/3.20	7/3.20	22.40	670.0	440	1110	105.16	0.1200
OSPREY	556.5	282.50	15.69	298.20	350	172	18/4.47	1/4.47	22.35	779.0	122	901	60.52	0.1017
PARAKEET	556.5	282.30	36.60	318.90	350	172	24/3.87	7/2.58	23.22	783.0	286	1069	88.29	0.1023
DOVE	556.5	282.60	45.92	328.50	350	172	26/3.72	7/2.89	23.55	783.0	359	1142	101.10	0.1022
EAGLE	556.5	282.10	65.82	347.90	350	172	30/3.46	7/3.46	24.21	784.0	515	1298	122.90	0.1026
PEACOCK	605	306.10	39.78	345.90	381	187	24/4.03	7/2.69	24.20	849.0	311	1160	95.86	0.0943
SQUAB	605	305.80	49.81	355.60	381	187	26/3.87	7/3.01	24.51	848.0	389	1237	109.60	0.0944
WOODDUCK	605	307.10	71.65	378.80	381	187	30/3.61	7/3.61	25.25	853.0	560	1413	129.00	0.0943
TEAL	605	307.10	69.62	376.70	381	187	30/3.61	19/2.16	25.24	853.0	545	1398	136.10	0.0943
KINGBIRD	636	323.00	17.95	341.00	400	197	18/4.78	1/4.78	23.90	891.0	140	1031	69.72	0.0890
ROOK	636	323.10	41.88	365.00	400	197	24/4.14	7/2.76	24.84	896.0	327	1223	101.00	0.0894
GROSBEAK	636	321.80	52.49	374.30	400	197	26/3.97	7/3.09	25.15	892.0	410	1302	111.90	0.0897
SCOTER	636	322.60	75.26	397.90	400	197	30/3.70	7/3.70	25.90	897.0	588	1485	135.50	0.0897
EGRET	636	322.60	73.54	396.10	400	197	30/3.70	19/2.22	25.90	897.0	576	1473	140.60	0.0897
FLAMINGO	666.6	337.30	43.72	381.00	419	206	24/4.23	7/2.82	25.34	935.0	342	1277	105.50	0.0856
GANNET	666.6	338.30	54.90	393.20	419	201	26/4.07	7/3.16	25.76	938.0	429	1367	117.30	0.0854
CROW	715.5	361.60	46.88	408.50	450	221	54/2.92	7/2.92	26.28	1003.0	366	1369	115.20	0.0799
STILT	715.5	363.30	46.88	410.20	450	222	24/4.39	7/2.92	26.32	1007.0	366	1373	113.30	0.0795
STARLING	715.5	361.90	59.15	421.10	450	221	26/4.21	7/3.28	26.68	1004.0	462	1466	125.90	0.0798
REDWING	715.5	362.10	82.41	444.50	450	221	30/3.92	19/2.35	27.43	1006.0	645	1651	153.70	0.0800

# ASTM B232


## Aluminium Conductor Steel Reinforced(ACSR)

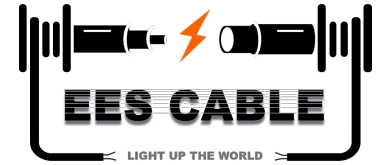

Co de Name	Area				Equivalent copper area		Stranding and wire diameter		Approx. overall diameter	Weight			Rated Strength	Maximum dc resistance at 20 °C
	Aluminium		Steel	Total			Aluminium	Steel		Aluminium	Steel	Total		
	AWG or MCM	mm <sup>2</sup>	mm <sup>2</sup>	mm <sup>2</sup>	AWG or MCM	mm <sup>2</sup>	mm	mm	mm	kg/km	kg/km	kg/km	kN	Ω/km
TERN	795	403.80	27.83	431.60	500	246	45/3.38	7/2.25	27.03	1120.0	217	1337	97.47	0.0715
CONDOR	795	402.30	52.15	454.50	500	245	54/3.08	7/3.08	27.72	1116.0	407	1523	124.30	0.0718
CUCKOO	795	402.30	52.15	454.50	500	245	24/4.62	7/3.08	27.72	1116.0	407	1523	123.80	0.0718
DRAKE	795	402.60	65.44	468.00	500	246	26/4.44	7/3.45	28.11	1116.0	511	1627	139.70	0.0717
MALLARD	795	403.80	91.78	495.60	500	246	30/4.14	19/2.48	28.96	1122.0	718	1840	171.20	0.0717
CRANE	874.5	442.50	57.36	499.90	550	270	54/3.23	7/3.23	29.07	1221.0	448	1669	136.70	0.0649
RUDDY	900	455.50	31.67	487.20	566	278	45/3.59	7/2.40	28.74	1268.0	247	1510	109.40	0.0634
CANARY	900	456.30	59.15	515.50	566	278	54/3.28	7/3.28	29.52	1265.0	462	1727	141.00	0.0633
RAIL	954	483.80	33.54	517.30	600	295	45/3.70	7/2.47	29.61	1342.0	262	1604	116.10	0.0597
CARDINAL	954	484.50	62.81	547.30	600	296	54/3.38	7/3.38	30.42	1343.0	491	1834	149.70	0.0596
ORLAN	1033.5	523.90	36.31	560.20	650	320	45/3.85	7/2.57	30.81	1453.0	283	1736	123.30	0.0551
CURLEW	1033.5	525.50	68.10	593.60	650	321	54/3.52	7/3.52	31.68	1457.0	532	1989	162.40	0.0550
BLUEJAY	1113	565.50	38.90	604.40	700	345	45/4.00	7/2.66	31.98	1568.0	304	1872	132.70	0.0511
FINCH	1113	565.00	71.57	636.60	700	345	54/3.65	19/2.19	32.85	1574.0	560	2134	174.60	0.0514
BUNTING	1192.5	605.80	41.90	647.70	750	370	45/4.14	7/2.76	33.12	1680.0	327	2007	142.40	0.0477
GRACKLE	1192.5	602.80	76.90	679.70	750	368	54/3.77	19/2.27	33.97	1680.0	601	2281	184.20	0.0481
BITTERN	1272	644.40	44.70	689.10	800	393	45/4.27	7/2.85	34.17	1787.0	349	2136	151.40	0.0448
PHEASANT	1272	645.10	81.71	726.80	800	394	54/3.90	19/2.34	35.10	1797.0	640	2137	194.10	0.0450
DIPPER	1351.5	684.20	47.20	731.10	850	417	45/4.40	7/2.92	35.16	1897.0	366	2263	160.30	0.0422
MARTIN	1351.5	685.40	86.70	772.10	850	418	54/4.02	19/2.41	36.17	1910.0	678	2588	206.10	0.0423
BOBOLINK	1431	725.20	50.10	775.40	900	442	45/4.53	7/3.02	36.24	2011.0	392	2403	168.60	0.0398
PLOVER	1431	726.90	91.80	818.70	900	443	54/4.14	19/2.48	37.24	2025.0	719	2744	218.40	0.0399
NUTHATCH	1510.5	764.20	52.80	817.00	950	466	45/4.65	7/3.10	37.20	2119.0	413	2532	177.60	0.0378
PARROT	1510.5	766.10	97.00	863.10	950	467	54/4.25	19/2.55	38.25	2134.0	760	2894	230.50	0.0379

# ASTM B232

## Aluminium Conductor Steel Reinforced(ACSR)

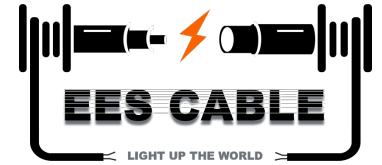

Code Name	Area			Equivalent copper area	Stranding and wire diameter		Approx. overall diameter	Weight			Rated Strength	Maximum dc resistance at 20°C		
	Aluminium		Steel		Total	Aluminium		Steel	Aluminium	Steel			Total	
	AWG or MCM	mm <sup>2</sup>	mm <sup>2</sup>		mm <sup>2</sup>	AWG or MCM		mm <sup>2</sup>	mm	mm			mm	kg/km
LAPWING	1590	804.10	55.60	859.80	1000	491	45/4.77	7/3.18	38.16	2230.0	424	2664	186.90	0.0359
FALCON	1590	806.20	102.40	908.70	1000	492	54/4.36	19/2.62	39.26	2246.0	802	3048	243.00	0.0360
CHUKER	1780	903.20	73.50	976.70	1119	551	84/3.70	19/2.22	40.70	2516.0	576	3092	227.80	0.0321
High Strength Strandings														
GROUSE	80	40.54	14.12	54.66	50	25	8/2.54	1/4.24	9.32	111.0	110	221	23.06	0.7089
PETREL	101.8	51.61	30.10	81.71	64	32	12/2.34	7/2.34	11.70	143.0	235	378	46.16	0.5595
MIORCA	110.8	56.11	32.73	88.84	70	34	12/2.44	7/2.44	12.20	155.0	256	411	50.19	0.5146
LEGHORN	134.6	68.20	39.78	108.00	85	42	12/2.69	7/2.69	13.46	189.0	311	500	60.67	0.4234
GUINEA	159	80.36	46.88	127.20	100	49	12/2.92	7/2.92	14.60	223.0	367	590	71.10	0.3593
DOTTEREL	176.9	89.41	52.15	141.60	111	55	12/3.08	7/3.08	15.40	248.0	408	656	76.68	0.3230
DORKING	190.8	96.51	56.30	152.80	120	59	12/3.20	7/3.20	16.00	267.0	440	707	82.77	0.2992
COCHIN	211.3	107.00	62.44	169.40	133	65	12/3.37	7/3.37	16.85	296.0	488	784	91.79	0.2698
BRAHMA	203.2	102.80	91.78	194.60	128	63	16/2.86	19/2.48	18.12	285.0	718	1003	126.52	0.2809